

Evidence for Strong-coupling S -wave Superconductivity in MgB_2 : ^{11}B NMR Study

H. Kotegawa¹, K. Ishida¹, Y. Kitaoka^{1,3}, T. Muranaka², and J. Akimitsu^{2,3}

¹*Department of Physical Science, Graduate School of Engineering Science,
Osaka University, Toyonaka, Osaka 560-8531, Japan*

²*Department of Physics, Aoyama-Gakuin University, Setagaya-ku, Tokyo 157-8572, Japan.*

³*Core Research for Evolutional Science and Technology (CREST) of the Japan Science and Technology Corporation (JST)*

(Dated: February 15, 2001)

We have investigated a gap structure in a newly-discovered superconductor, MgB_2 through the measurement of ^{11}B nuclear spin-lattice relaxation rate, $^{11}(1/T_1)$. $^{11}(1/T_1)$ is proportional to the temperature (T) in the normal state, and decreases exponentially in the superconducting (SC) state, revealing a tiny coherence peak just below T_c . The T dependence of $1/T_1$ in the SC state can be accounted for by an s -wave SC model with a large gap size of $2\Delta/k_B T_c \sim 5$ which suggests to be in a strong-coupling regime.

PACS numbers: 74.25.-q, 74.72.-b, 76.60.-k, 76.60.Es

Quite recently, Akimitsu and co-workers have discovered a new superconducting (SC) material MgB_2 that reveals a remarkably high SC transition temperature of $T_c \sim 40$ K [1]. MgB_2 crystallizes in the hexagonal AlB_2 -type structure, consisting of alternating hexagonal layers of Mg atoms and graphite-like layers of B atoms. The discovery of superconductivity with a relatively high value of T_c in this compound gives a new impact in the solid state physics, since it may give other possibility for finding the high- T_c superconductivity in some binary inter-metallic compounds besides cuprates and C_{60} -based compounds. It may be promising to discover new compounds with a high- T_c value exceeding the liq.- N_2 temperature other than cuprates. Soon after the discovery, Bud'ko and co-workers reported that T_c increases from 39.2 K for Mg^{11}B_2 to 40.2 K for Mg^{10}B_2 , giving a clear indication that electron-phonon interactions are playing an important role [2]. However, the observed high T_c value of this compound seems to be either beyond or at a limitation for the phonon-mediated superconductivity that was predicted theoretically several decade ago[3]. Therefore we speculate on that a new exotic mechanism might be possible for the occurrence of the high- T_c superconductivity in MgB_2 . In order to gain an insight into a possible mechanism, it is quite important to understand its pairing symmetry and a SC-gap structure.

In this letter, we report ^{11}B -NMR study that has shed light on the above issues. Spin-lattice relaxation rate ($1/T_1$) of ^{11}B has been measured in a temperature (T) range of 15 - 260 K. We have found a $T_1 T = \text{constant}$ behavior in the normal state, and an exponential decrease of $1/T_1$ that was accompanied with a tiny coherence peak in the SC state. From the T dependence of $1/T_1$ in the SC state that is consistent with an s -wave model with a larger isotropic gap of $2\Delta/k_B T_c \sim 5$ than the BCS value of 3.5, the superconductivity in MgB_2 is concluded to be in a strong coupling regime and suggested to be mediated by strong-electron phonon interactions.

A polycrystalline sample of MgB_2 was prepared as in reference[4]. Electric resistivity and DC magnetization show the SC transition at 39 K. The bulk sample with-

out powdering has been used for NMR measurements to avoid some crystal defects if any. T_1 was measured by monitoring the nuclear magnetization after a saturation rf-pulse under an external field $H = 13.5$ kOe at a frequency $f = 18.5$ MHz in the normal state and $H = 44.2$ kOe at $f = 60.4$ MHz in the SC state. $T_c = 29$ K under $H = 44.2$ kOe was determined from an ac-susceptibility that was measured using an "in-situ" NMR coil, as shown in an inset of Fig.1. The result is in good agreement with the references reported recently[5, 6].

^{11}B -NMR spectrum has a simple shape with a full width at the half maximum of ~ 10 Oe. Its resonance peak does not show any T dependence in the normal state within an experimental error of 2 Oe. T_1 measured at the peak in spectrum was determined by fitting the relaxation function of the nuclear magnetization $m(t)$ to the following theoretical two-exponential form,[7]

$$\begin{aligned} m(t) &= \frac{M(\infty) - M(t)}{M(\infty)} \\ &= \frac{1}{10} \exp\left(-\frac{t}{T_1}\right) + \frac{9}{10} \exp\left(-\frac{6t}{T_1}\right). \end{aligned} \quad (1)$$

Here $M(t)$ is the nuclear magnetization at time t after saturation pulses. From good fits to this formula, T_1 was precisely determined over a measured T range, although a short component of T_1 appears at low temperatures below 20 K, associated with the presence of vortex cores in the mixed state.

Figure 1 shows the T dependence of $1/T_1$ in the T range of 15 - 260 K. In the normal state, $1/T_1$ obeys a $T_1 T = \text{constant}$ relation with $T_1 T = 1.8 \times 10^2$ (s · K) down to T_c . In the SC state, we have found a tiny coherence peak in $1/T_1$ just below T_c , followed by an exponential decrease of $1/T_1$.

In general, $1/T_1$ in the SC state is related to the density of states (DOS) in the SC state, $N_s(E)$ as follow,

$$\frac{1}{T_1} \propto \int_0^\infty (N_s(E)^2 + M(E)^2) f(E)(1 - f(E)) dE \quad (2)$$

where $M(E)$ and $f(E)$ are the so-called "anomalous" DOS arising from the coherence effect of scattering inherent to a spin-singlet SC state and the Fermi-distribution

function, respectively [8]. Note $M(E) = 0$ in the case of spin-triplet pairing state. The T dependence of $1/T_1$ is calculated by using a typical s -wave model where a phenomenological energy broadening function in $N_s(E)$ is assumed to be of a rectangle type with a width 2δ and a height $1/2\delta$ as presented by Hebel [9]. A calculation is shown by a solid curve in Fig.1. The T dependence of $1/T_1$ except just below T_c can be well reproduced by the calculation that assumes the SC gap size of $2\Delta/k_B T_c \sim 5$ and $\delta/\Delta(0) \sim 1/3$. It should be noted that the T dependence of $1/T_1$ cannot be reproduced by a model of the spin-triplet Balian-Werthamer (BW) state with an isotropic gap [10], therefore the spin-triplet state should be ruled out. Remarkable findings of the tiny coherence peak in $1/T_1$ just below T_c that is followed by the exponential decrease below $0.8 T_c$ provide convincing evidence for the spin-singlet s -wave pairing realized in MgB_2 . The SC-gap value larger than the weak-coupling BCS value suggests that the superconductivity in MgB_2 is in a strong coupling regime. The strong electron-phonon coupling may give rise to some intense lifetime broadening of quasiparticles just below T_c , suppressing the coherence peak more substantially than a behavior expected from the calculation. The T dependence of $1/T_1$ in the SC state of MgB_2 is quite similar to that in Chevrel-phase compound $\text{TlMo}_6\text{Se}_{7.5}$ with $T_c = 12.2 \text{ K}$ [11]. Therefore we conclude that the superconductivity in MgB_2 is of a strong-coupling s -wave type with the larger value $2\Delta/k_B T_c \sim 5$ than the weak coupling BCS one.

Present results of $1/T_1$ in MgB_2 are in quite contrast with that in cuprates such as $\text{La}_{1.85}\text{Sr}_{0.15}\text{CuO}_4$ that reveals a comparable T_c value of 38 K [12]. The $1/T_1 T$ in the cuprates shows a Curie-Weiss behavior in the nor-

mal state, which evidences that the superconductivity appears on the verge of the antiferromagnetism. $1/T_1$ in the SC state decreases sharply without the coherence peak just below T_c , followed by a T^3 dependence far below T_c . This evidences that the symmetry of the Cooper pairs is of a d -wave type with a line-node gap. Various experiments that were reported so far tell us that the Cooper pairs are presumably mediated via magnetic interactions other than electron-phonon interactions. On the other hand, the T dependence of $1/T_1$ in MgB_2 shows that magnetic correlations are absent in the normal state and that the SC state is characterized by the large isotropic gap that is consistent with the strong coupling s -wave superconductor. In this context, it is natural to consider that the mechanism of the superconductivity in MgB_2 is quite different from in cuprates. Rather the electron-phonon interactions may play an important role. We suggest that the high value of T_c in MgB_2 may be due to the strong electron-phonon coupling via some phonon modes inherent to a light element of boron.

In conclusion, we report that the $1/T_1$ of ^{11}B decreases exponentially in the SC state, revealing a tiny coherence peak just below T_c . The T dependence of $1/T_1$ in the SC state can be accounted for by a spin-singlet s -wave model where $2\Delta/k_B T_c \sim 5$ is substantially larger than the weak coupling BCS value of 3.5. It is suggested that the strong electron-phonon interaction may play an important role for the high temperature superconductivity in MgB_2 .

We are grateful for helpful discussion with G.-q. Zheng. This work was supported by the COE Research (10CE2004) in Grant-in-Aid for Scientific Research from the Ministry of Education, Sport, Science, and Culture of Japan.

-
- [1] J. Akimitsu, Symposium on Transition Metal Oxides. Sendai, January 10, 2001.
 - [2] S. L. Bud'ko *et al.*, to be published in Phys. Rev. Lett.
 - [3] W. L. McMillan, Phys. Rev. **167**, 331 (1968).
 - [4] J. Nagamatsu *et al.*, submitted to Nature.
 - [5] D. K. Finnemore *et al.*, cond-mat/0102114.
 - [6] Y. Takano *et al.*, cond-mat/0102167.
 - [7] A. Narath, Phys. Rev. **167**, 162 (1967).
 - [8] D. E. MacLaughlin, in *Solid State Physics*, edited by

- H. Ehrenreich, F. Seitz, and D. Turbull (Academic, New York, 1976), Vol. 31.
- [9] L. C. Hebel, Phys. Rev. **116**, 79 (1959).
- [10] R. Balian and N. R. Wertheramer, Phys. Rev. **131**, 1553 (1963).
- [11] S. Ohsugi *et al.*, J. Phys. Soc. Jpn. **61**, 3054 (1992).
- [12] K. Ishida *et al.*, J. Phys. Soc. Jpn. **58**, 36 (1989).

FIG. 1: T dependence of $^{11}(1/T_1)$ in MgB_2 . Closed and open circles correspond to $1/T_1$ measured in the external field of 44.2 kOe and 18.5 kOe, respectively. A solid curve in the SC state shows the calculation using the typical s -wave model (see text)[9]. The inset shows T dependence of ac -susceptibility in 44.2 kOe measured by an *in-situ* NMR coil. The arrows show an onset of the superconductivity under 44.2 kOe.

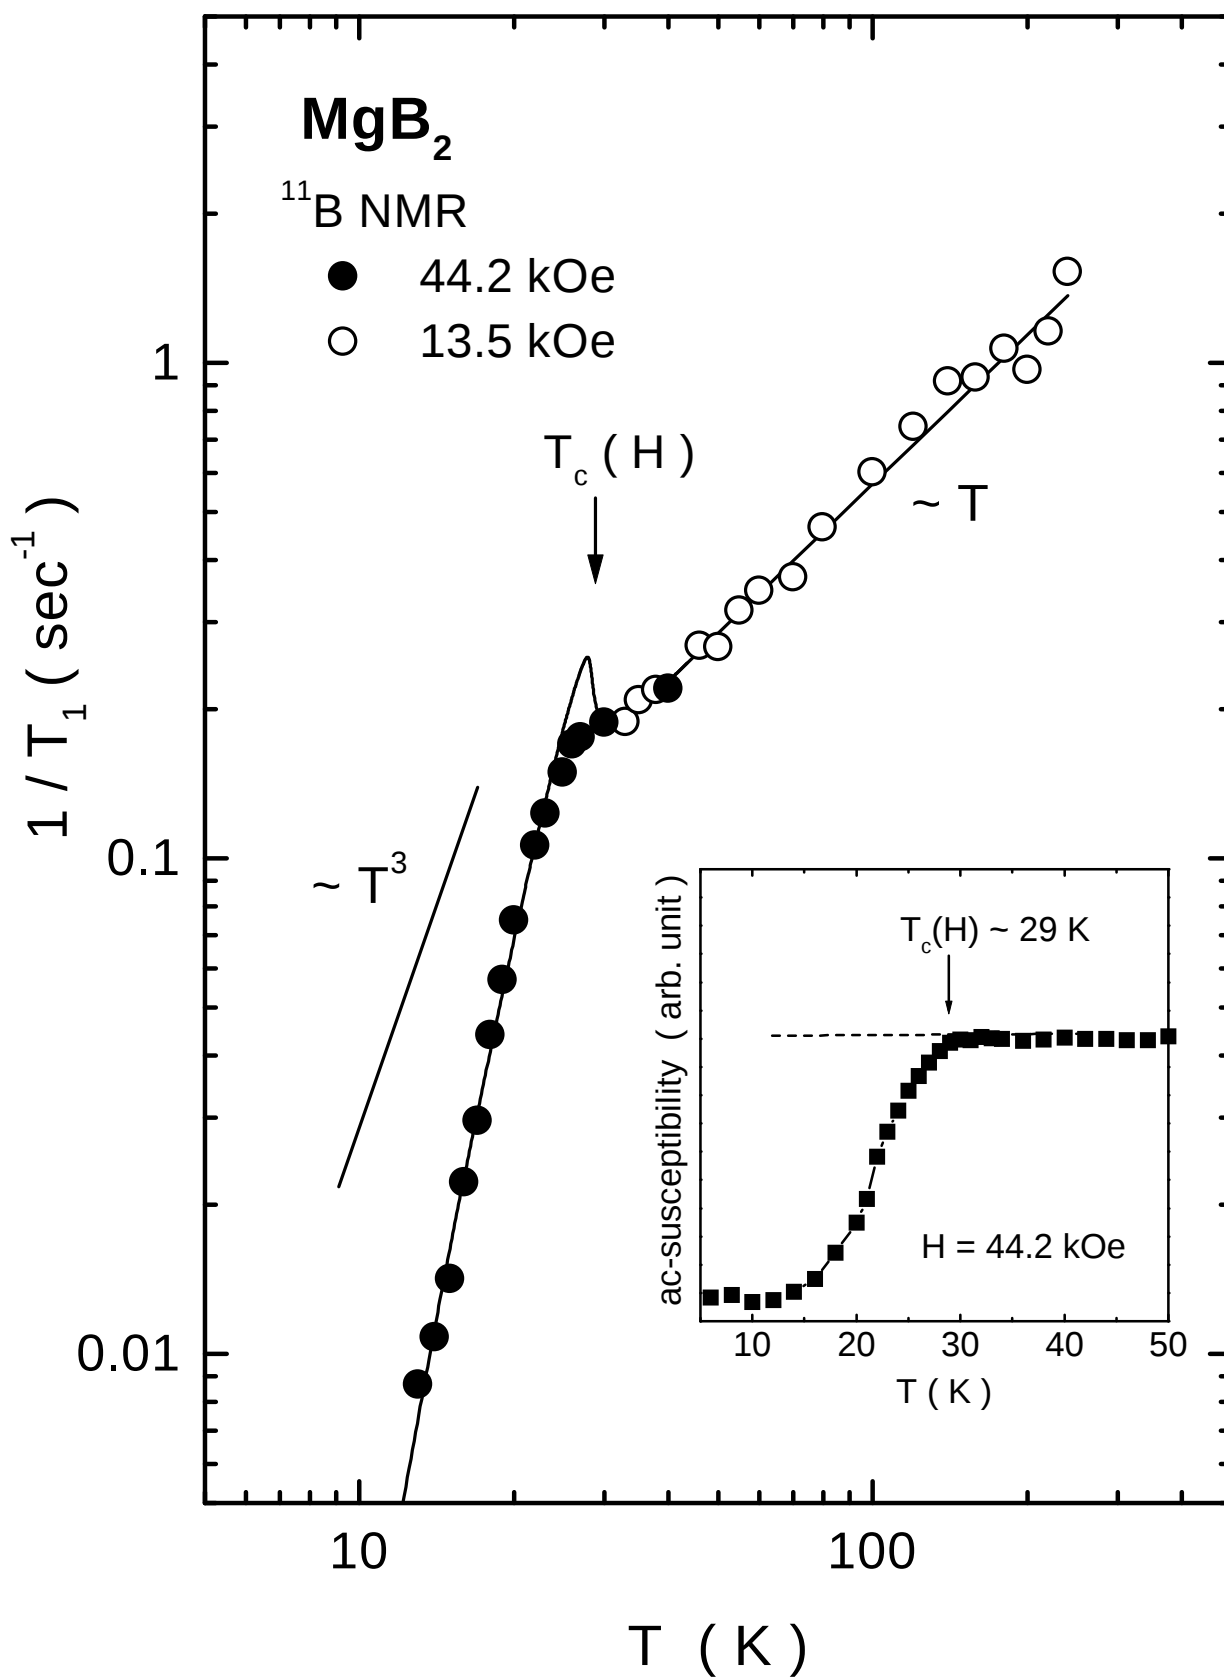


Fig. 1 : Kotegawa *et al.*